

Evaluation of Wear Properties of CNT and Eglass fiber reinforced aluminium metal matrix composites

Murali R^{*1}, Dr. Shivarudraiah², Dr. H K Shivanand², Manjunatha³, Prashanth⁴

PG Scholar, Mechanical Engineering, UVCE, Bengaluru, India^{1,3,4}

Professor, Mechanical Engineering, UVCE, Bengaluru, India²

Abstract: In the current industrial scenario, composite materials have lot of scope due to its improved mechanical properties like hardness, toughness, compressive strength & tensile strength. Conventional monolithic materials have limitations with respect to composite materials. Development of hybrid metal matrix composites has become an important area of research interest in Material Science.

The Main objective of this work is to develop “Carbon Nano tubes and E-Glass Fiber Reinforced Aluminium Al-7075 Hybrid Metal Matrix Composite (AHMMC)” and to evaluate the properties of these hybrid composites developed. The different types of Hybrid Composites are fabricated with varying composition of Carbon Nano Tubes and E Glass Fiber and the specimens are prepared as per ASTM Standards and experiments are conducted for characterization of Wear Properties at different Speed with varying loading condition.

Keywords: Metal Matrix Composites, Wear, Carbon Nano tubes, E Glass and Aluminum alloy.

I. INTRODUCTION

The possibility of taking advantage of particular properties of the constituent materials to meet specific demands is the most important motivation for the development of composites. A composite is a material made with several different constituents intimately bonded. When it comes to composites, the terms matrix and reinforcement are often used. The matrix is a percolating “soft” phase (with in general excellent ductility, formability and thermal conductivity) in which are embedded the “hard” reinforcements (high stiffness and low thermal expansion). The reinforcements can be continuous or discontinuous, orientated or disorientated. The composites are classified by:

- Their matrix (polymer, ceramic, metal).
- Their reinforcement, which includes the chemical nature (oxides, carbides, nitrides), shape (continuous fibres, short fibres, whiskers, particulates) and orientation.
- Their processing routes.

Aluminium is the most popular matrix for the metal matrix composites (MMCs). The Al alloys are quite attractive due to their low density, their capability to be strengthened by precipitation, their good corrosion resistance, high thermal and electrical conductivity, and their high damping capacity. Aluminium matrix composites (AMCs) have been widely studied since the 1920s and are now used in sporting goods, electronic packaging, amours and automotive industries. They offer a large variety of mechanical properties depending on the chemical composition of the Al-matrix. Like all composites, Aluminium-matrix composites are not a single material but a family of materials whose stiffness, strength, density, thermal and electrical properties can be tailored. The matrix alloy, reinforcement material, volume and shape of the reinforcement, location of the reinforcement and fabrication method can all be varied to achieve required properties. The aim involved in designing metal matrix composite materials is to combine the desirable attributes of metals and ceramics. The addition of high strength, high modulus refractory particles to a ductile metal matrix produce a material whose mechanical properties are intermediate between the matrix alloy and the ceramic reinforcement. Metals have a useful combination of properties such as high strength, ductility and high temperature resistance, but sometimes have low stiffness, whereas ceramics are stiff and strong, though brittle.

Metal Matrix Composites (MMC)

Metal matrix composites are composed of a metallic matrix (aluminum, magnesium, iron, cobalt, copper) and a dispersed ceramic (oxides, carbides) or metallic (lead, tungsten, molybdenum) phase. Metal matrix composites, at present though generating a wide interest in research fraternity, are not as widely in use as their plastic counterparts. High strength, fracture toughness and stiffness are offered by metal matrices than those offered by their polymer counterparts. They can withstand elevated temperature in corrosive environment than polymer composites. Most metals

and alloys could be used as matrices and they require reinforcement materials which need to be stable over a range of temperature and non-reactive too. However, the guiding aspect for the choice depends essentially on the matrix material. Light metals form the matrix for temperature application and the reinforcements in addition to the aforementioned reasons are characterized by high moduli.

Most metals and alloys make good matrices. However, practically, the choices for low temperature applications are not many. Only light metals are responsive, with their low density proving an advantage. Titanium, Aluminium and magnesium are the popular matrix metals currently in vogue, which are particularly useful for aircraft applications. If metallic matrix materials have to offer high strength, they require high modulus reinforcements. The strength-to-weight ratios of resulting composites can be higher than most alloys. The melting point, physical and mechanical properties of the composite at various temperatures determine the service temperature of composites. Most metals, ceramics and compounds can be used with matrices of low melting point alloys. The choice of reinforcements becomes more stunted with increase in the melting temperature of matrix materials.

MMCs are made by dispersing a reinforcing material into a metal matrix. As the name implies, for Metal-Matrix Composites (MMCs), the matrix is a ductile metal. These materials may be utilized at higher service temperatures than their base metal counterparts; furthermore, the reinforcement may improve specific stiffness, specific strength, abrasion resistance, creep resistance, thermal conductivity, and dimensional stability.

Some of the advantages of these materials over the polymer matrix composites include:

- Higher operating temperatures
- No flammability
- Do not absorb moisture
- Have better electrical and thermal conductivity
- Are resistant to radiation damage
- Greater resistance to degradation by organic fluids

Low cost, therefore, their (MMC) use is somewhat restricted. In polymeric composites, matrix materials play important but secondary role of holding the fibers in place and providing proper load dispersion in the fibers, while material strength and stiffness are controlled by the reinforcements. By contrast, mechanical properties of metal matrix composites are controlled by the matrix to a considerably larger extent, though fibers still provide the main contribution to strength and stiffness of the material. The super alloys, as well as alloys of aluminum, magnesium, titanium, and copper, are employed as matrix materials. The reinforcement may be in the form of particulates, both continuous and discontinuous fibers, and whiskers; concentrations normally range between 10 and 60 vol. %.

Continuous fiber materials include carbon, silicon carbide, boron, alumina, and the refractory metals. On the other hand, discontinuous reinforcements consist primarily of silicon carbide whiskers, chopped fibers of alumina and carbon, and particulates of silicon carbide and alumina. In a sense, the cermets fall within this MMC scheme. In the automotive industry, MMCs have been used commercially in fiber reinforced pistons and particle-strengthened brake disks.

Aerospace structural applications include advanced aluminum alloy metal matrix composites. Boron fibers are used as the reinforcement for the Space Shuttle Orbiter, and continuous graphite fibers for the Hubble Telescope. Reinforcements for metal matrix composites have a manifold demand profile, which is determined by production and processing and by the matrix system of the composite material. The following demands are generally applicable

- Low density
- Mechanical compatibility (a thermal expansion coefficient which is low but adapted to the matrix)
- Chemical compatibility
- Thermal stability
- High Young's modulus
- High compression and tensile strength
- Good process ability
- Economic efficiency

Which components are finally used, depends on the selected matrix and on the demand profile of the intended application.

Aluminum Matrix Composites (AMC)

Magnesium Matrix Composite

Copper Matrix Composite

Titanium Matrix Composite

Aluminium as such is a light weight material and available at low costs, but employing plain aluminium into automotive could be a disadvantage because of weak bonding of the matrix which is intolerant towards mechanical stresses. Henceforth, it becomes necessary to introduce other materials into the aluminium matrix to make it a better option for various applications.

Current work has utilized this lacuna to bring out a more feasible Aluminium composite which is reinforced with other economically available materials like CNT, E Glass to produce good quality stress resistant composite material. A lot of research has been done on aluminum alloy 1XXX to aluminum 6XXX based composites but research on aluminum alloy 7XXX based composites is very rare, also the properties of these composites are still not clear. Against this background, the present research work has been undertaken, with an objective to study the effect of different composition of reinforcement as E-Glass and CNT on the Al 7075 based metal matrix composites.

II. MATERIALS AND METHOD

A. Material used

• Graphene

Graphene is a crystalline allotrope of carbon with 2-dimensional properties. Its carbon atoms are densely packed in a regular atomic-scale chicken wire (hexagonal) pattern. Each atom has four bonds, one σ bond with each of its three neighbours and one π - bond that is oriented out of plane. The atoms are about 1.42 Å apart. Graphene's hexagonal lattice can be regarded as two interleaving triangular lattices. This perspective was successfully used to calculate the band structure for a single graphite layer using a tight-binding approximation.

• Kenaf fiber

The kenaf fiber derived from the outer fibrous bark is also known as bast fibre. Kenaf bast fiber has superior flexural strength combined with its excellent tensile strength that makes it the material of choice for a wide range of extruded, moulded and non-woven products. Kenaf fiber could be utilized as reinforcement material for polymeric composites as an alternative to glass fiber.

• Banana fiber

Banana fiber a ligno-cellulosic fiber obtained from the pseudo-stem of banana plant (*Musa sepientum*) is a bast fiber with relatively good mechanical properties are shown in the table 4.4. In the recent past, banana fiber as shown in fig had a very limited application and was primarily used for making items like ropes, mats, and some other composite materials.

• Glass fiber

Glass or electrical grade glass was originally developed for standoff insulators for electrical wiring. It was later found to have excellent fiber forming capabilities and is now used almost exclusively as the reinforcing phase in the material commonly known as fiber glass. Glass fibers shown in fig are generally produced using melt spinning techniques. These involve melting the glass composition into a platinum crown which has small holes for the molten glass to flow.

• Epoxy resin

The epoxide group can be referred to as a glycidyl group. The resins are adaptable in nature, especially in erosion to opposition, high quality to weight proportion, adhesion properties and dimensional dependability. They are the polymers that are normally made up by methods for gathering epichlorhydrin with bisphenol A. The resins are shaped at temperatures in the locale of 50-100°C because of the way that the consistency is high, so that because of this, they disintegrate in an inert solvent dissolvable to limit the thickness with the goal that cover at encompassing temperature is conceivable.

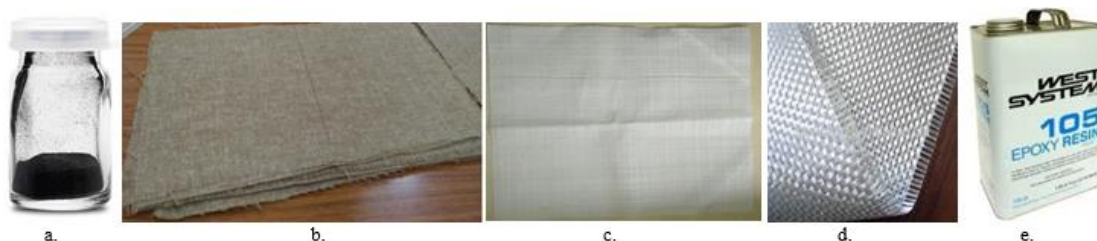


Fig 1: a) Graphene powder, b) Kenaf fabric mat, c) Banana fabric mat, d) Glass fabric mat, e) Epoxy resin.

B. Fabrication Technique

Hand lay-up technique is basically an open moulding that is suited for fabricating from small to large variety of composites. Through it is lesser in terms of production volume per mould, it is possible to make up the composites in large quantities using multiple stamps. The hand lay technique is the most basic type of fabrication which in a sample in the process, offers varying ranges of sizes and also provides tooling at low price, however skilled operators are needed to obtain the consistency in quality and good production rates. The changes in design can be made at the spot with a minimum share for the equipment.



Fig 2: Hand lay-up technique process

A. Materials

Reinforcement's compositions are selected based on the previous work done by many researchers. In many literatures authors have mentioned the reinforcement percentage should be less than 10% for E-Glass and 2% for CNT, if it is more than 10% reinforcement will not mix with the casting properly and there is a chance of agglomeration of particles. So, in the present study reinforcement compositions are limited to above mentioned wt. %.

Table 1: Details of Materials Procured

Material	Manufacturer/Suppliers	Quantity
Al 7075 alloy	FENFE METALLURGICALS located at Uttarahalli, Bangalore	50 kg
E-Glass fiber	Suntech fiber india pvt. Ltd, Vasanth nagar, bangalore.	2 kg
CNT	United nanotech innovations pvt. Ltd. Hosakote, bangalore	600 g

B. Fabrication method

The microstructure of any material is a complex function of the casting process, subsequent cooling rates. Therefore, composites fabrication is one the most challenging and difficult task. Stir casting technique of liquid metallurgy was used to prepare Al 7075 and Al 7075 Hybrid composites.

Al based MMC preparation by Stir Casting

A schematic of stir casting setup is as shown in figure, It consists of a coke fired furnace and a stirrer assembly, which was used to synthesize the composite.

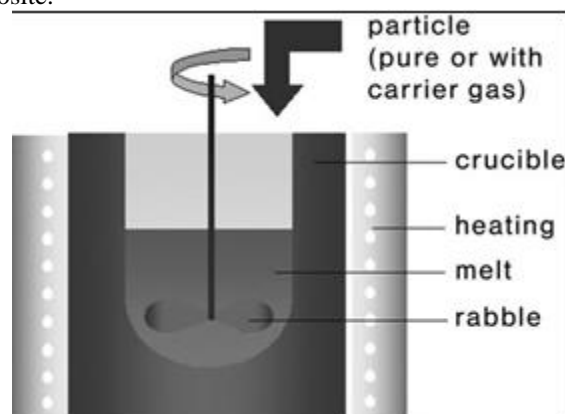


Fig 3: Graphical representation of stir casting

Table 2: Composition of Cast Hybrid Metal Matrix Composite


Composite Designation	E-Glass %	CNT %	% Al 7075
C1	0	0	100
C2	1	0.5	98.5
C3	1	1.0	98
C4	1	1.5	97.5
C5	1	2.0	97
C6	5	0.5	94.5

C7	5	1.0	94
C8	5	1.5	93.5
C9	5	2.0	93

III. EXPERIMENTATION

Wear Test

The wear test was conducted using a pin-on-disc computerized wear testing machine in accordance with ASTM standards. The surface finish of the specimens (Ra) 2µm was rubbed against a hardened steel disc, which has a better surface finish of (Ra) 0.2µm. The test uses the specimens of diameter of 6mm and length 35mm machined from the cast specimens. The wear tests were conducted using loads of 2, 4 kg in steps of 2 kg at 300 rpm, 400 rpm and 500 rpm and 4 kg at 400 rpm and 500 rpm. The test period was taken to be 10 minutes and the track radius selected was 50mm. The apparatus consists of a steel disc of 50 mm diameter which forms the counter face on which the test specimens or the pins slide over. The wear test was also conducted for the cast specimens of Aluminium 7075 alloy with varying percentage of CNT (0.5%, 1%, 1.5%, 2%) and E-glass fibers (1%, 5%) in a cast conditions and were assessed for wear resistance. The wear results of as cast hybrid composites with different compositions of reinforcements at varying sliding speeds and different loads are shown in the tabulations.

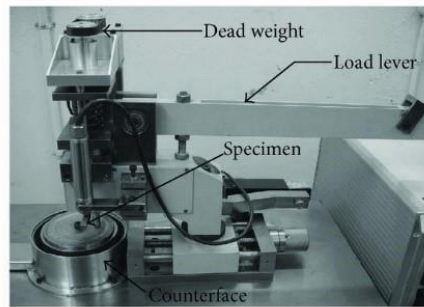

4Fig 4: Pin-on-Disk Machine


IV. RESULTS

Wear Test Results


Wear may be defined as damage to a solid surface caused by the removal or displacement of material by the mechanical action of a contacting solid, liquid or gas. It may be significant surface damage and the damage is usually thought of as gradual deterioration. Wear rate and percentage of wear decreases greatly for specific proportion of CNT as 0.5% and 5% E-glass and in small proportion for CNT (1% & 1.5%) and E-glass (1 & 5%). The significant improvement in wear resistance of the composite may be due to size of reinforcement or dispersion of reinforcement used, it is generally found that the benefits of reinforcement are greater for increase in the content of reinforcement. The results of wear are tabulated in the respected tables and represented in the graphs. The variation of wear properties is ascertained by conducting test for different wear loads of 2 Kg and 4 Kg and at different speeds of 300 rpm, 400 rpm and 500 rpm.

After performing Hardness and Wear test for different weight percentages of CNT and E-glass, we find that the wear rate of the composite decreases as the percentage of CNT increases from 0.5 % to 1.5%. Above 1.5 %, the wear rate increases drastically. The use of CNT and E-glass as reinforcement materials at a specified proportion increases the hardness and decreases the wear rate.


The E-glass of 1% added as reinforcement to AA-7075 decreases the density of the composite and in turn decreases the ductility. As the percentage of E-glass increases to 5%, the density of the composite increases meagerly. The experimental results are quite acceptable and from this conclusion can be drawn.

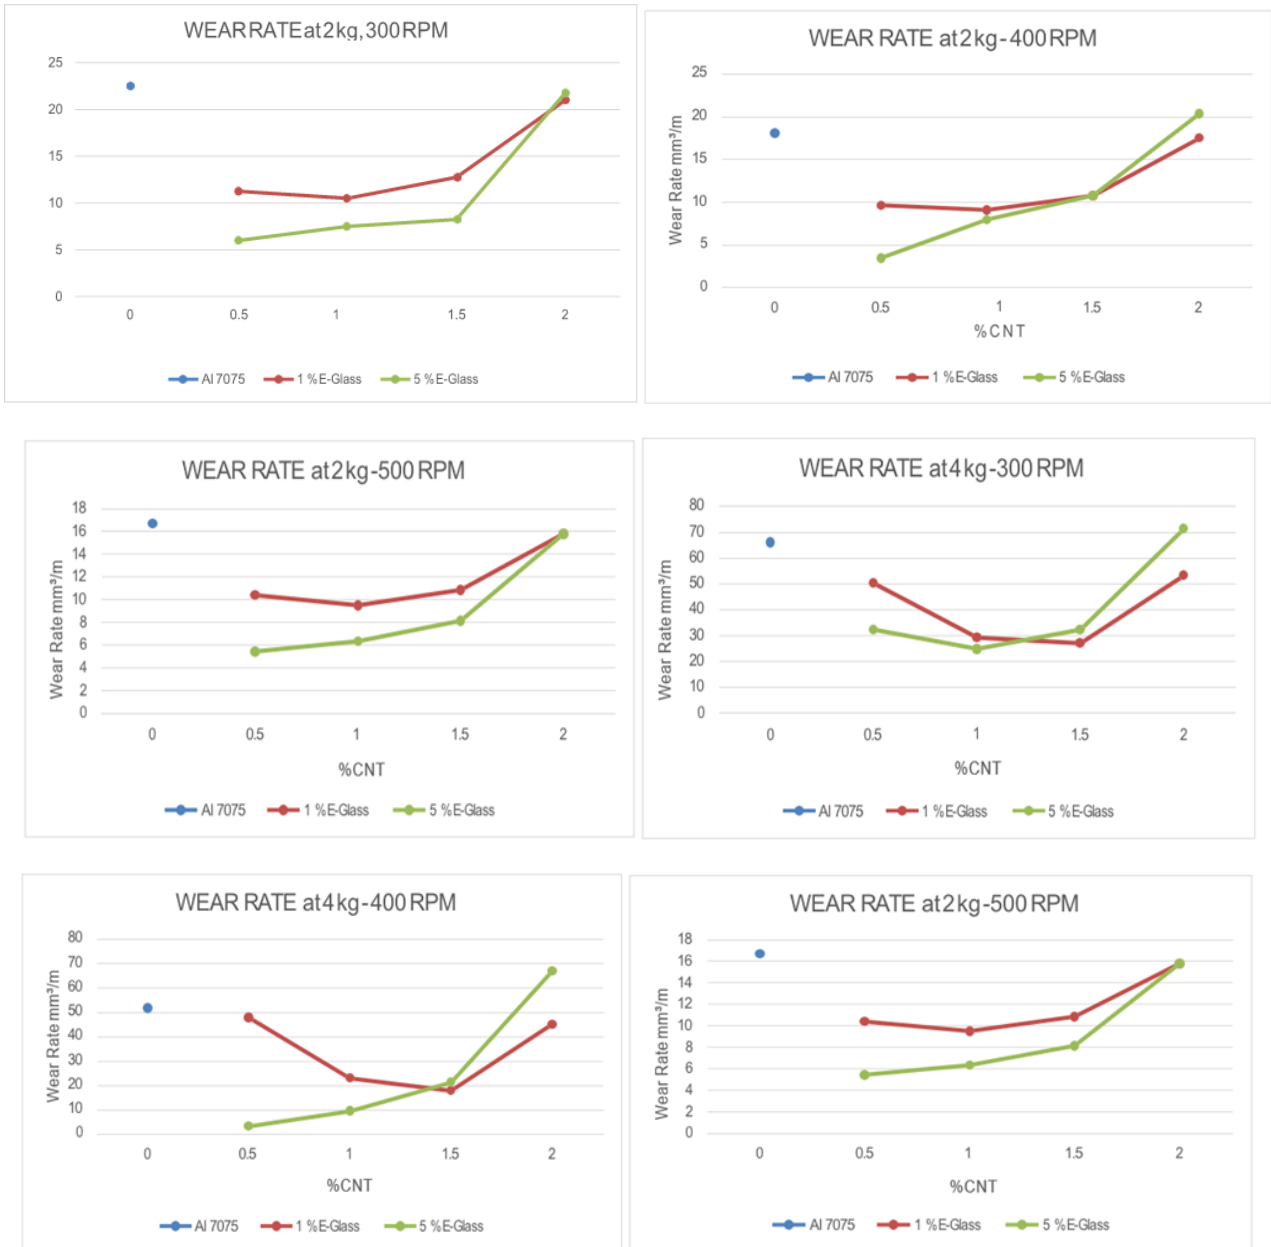

Graph: Wear Rate of 2kg and 4kg at 300,400,500RPM respectively.

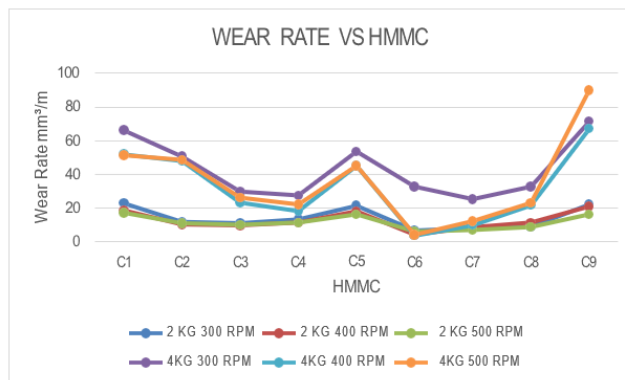

Graph 2 (a) Wear rate of HMMC at 2 kg 300RPM, 2 kg 400RPM, 2 kg 500RPM, 4 kg 300 RPM, 4 kg 400 RPM and 4 kg 500 RPM

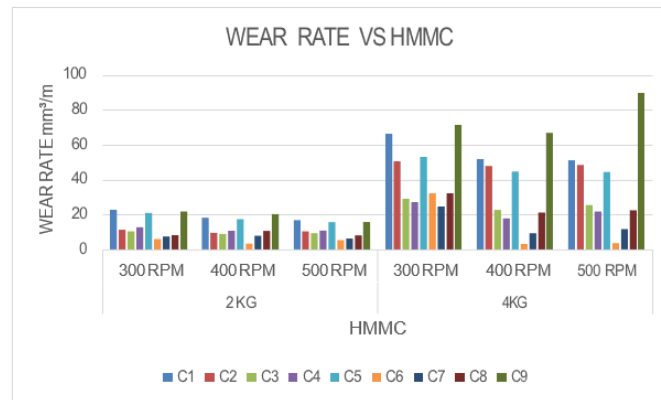

Graph 2 (b) Comparison chart of Wear rate of HMMC at 2kg 300 RPM, 2 kg 400 RPM, 2 kg 500 RPM, 4 kg 300 RPM, 4 kg 400 RPM and 4 kg 500 RPM...

V. CONCLUSION

in this present research work we take part the exploration of a new Hybrid composite material and finally fabricated an Al 7075 reinforced with E-Glass and CNT hybrid metal matrix composite. Newly developed metal underwent through different test to determine its properties. After brainstorming, we arrived into the following conclusions.

- Wear rate found to be decreased with increase in weight percentage of E-Glass and CNT to Al 7075. Wear rate of HMMC is less compared to base matrix Al 7075.
- Addition of E-glass enhances the wear resistance property compared to CNT in Al 7075.
- Incorporation of reinforcements E-Glass and CNT to Al 7075 matrix effects in less wear rate under various speed conditions at a load of 2Kg, 4Kg
- The sliding speed increases that causes ineffective contact between the surfaces of the hybrid composite which results reduction in wear rate.
- At 2kg and 300rpm the wear rate of Al 7075 hybrid MMC diminishes with 0.5% CNT and 5% E glass. The wear rate has diminished by 73.33% contrasted to Al 7075.
- At 2kg and 400rpm the wear rate of Al 7075 hybrid MMC diminishes with 0.5% CNT and 5% E glass. The wear rate has diminished by 81.25% contrasted to Al 7075.
- At 2kg and 500rpm the wear rate of Al 7075 hybrid MMC diminishes with 0.5% CNT and 5% E glass. The wear rate has diminished by 67.58% contrasted to Al 7075.
- At 4kg and 300rpm the wear rate of Al 7075 hybrid MMC diminishes with 1% CNT and 5% E glass. The wear rate has diminished by 62.51% contrasted to Al 7075.
- At 4kg and 400rpm the wear rate of Al 7075 hybrid MMC diminishes with 0.5% CNT and 5% E glass. The wear rate has diminished by 93.89% contrasted Al 7075.
- At 4kg and 500rpm the wear rate of Al 7075 hybrid MMC diminishes with 0.5% CNT and 5% E glass. The wear rate has diminished by 92.92% contrasted to Al 7075.
- It is arrived into conclusion that the best hybrid metal matrix composite (HMMC) is C6 among all other developed HMMC. It consists of 0.5% CNT, 5% E-glass and Al 7075. Wear rate is reduced by 93.88% at 4kg load and 400rpm.

REFERENCES

- [1]. R.S. Raveendra, P.V. Krupakara, P.A. Prashanth, B.M. Nagabhushana "Enhanced Mechanical Properties of Al- 6061 Metal Matrix Composites Reinforced with α -Al₂O₃ Nano ceramics" journal of Materials Science & Surface Engineering Vol. 4 (7), 2016, pp 483-487.
- [2]. Miss. Laxmi, Mr. Sunil Kumar "Fabrication and Testing of Aluminium 6061 Alloy & Silicon Carbide Metal Matrix Composites" International Research Journal of Engineering and Technology (IRJET) Volume: 04 Issue: 06 | June-2017.
- [3]. Z. Hasan, R. K. Pandey, D.K. Sehgal "Wear Characteristics in Al-SiC Particulate Composites and the Al-Si Piston Alloy" Journal of Minerals & Materials Characterization & Engineering, Vol. 10, No.14, pp.1329-1335, 2011.
- [4]. Bhoopathiraam, Sreenivas Rao K.V, Vasudeva B, "Effect of boron carbide reinforced Nano Aluminum matrix composites" IJMMSE, ISSN 2278-2516, Vol.3, Issue 1, Mar 2013, 41-48
- [5]. Perez-Bustamante R., Bueno-Escobedo J.L., Jimenez-Lobato J., Estrada-Guel I., Miki-Yoshida M., Licea-Jimenez L. and Martinez-Sanchez R. (2012): "Wear behaviour of Al₂O₃-CNTs composites synthesized by mechanical alloying", Wear, Vol.292-293, PP 169-175.
- [6]. AfsanehDorri Moghadam, Emad Omrani, Pradeep L. Menezes and Pradeep K. Rohatgi (2015): "Mechanical and tribological properties of self-lubricating metal matrix nanocomposites reinforced by carbon nanotubes (CNTs) and graphene", Composites Part B, Vol. 77, PP 402-420.
- [7]. Rita Maurya, Binit Kumar, Ariharana S., Ram Kumar J and Kantesh Balania (2016): "Effect of carbonaceous reinforcements on the mechanical and tribological properties of friction stir processed Al6061 alloy", Materials and Design, Vol. 98, PP 155-166
- [8]. E. Naveen, B. Vijaya Ramnath, C. Parswajinan, K. Pradeep & S. Sanjay Arun Investigation on Wear Behaviour of CNT Reinforced Al-SiC Metal Matrix Composites, 182International Journal of Vol. 9, Issue 3, Jun 2019, 171- 176
- [9]. I. Sridhar Karthick R. Narayanan "Processing and characterization of MWCNT reinforced aluminium matrix composites" J Mater. Sci., 44(2009) pp. 1750-1756
- [10]. Deng C.F., Zhang X., Ma Y., Wang D., 2007, Fabrication of aluminium matrix composite reinforced with carbon nanotubes, Rare Metals, 26(5), 450-455